

VOL III

THE GREAT WORLD OF NANOTECHNOLOGY

Emilio Castro Otero
(Organizador)

 EDITORA
ARTEMIS
2025

VOL III

THE GREAT WORLD OF NANOTECHNOLOGY

Emilio Castro Otero
(Organizador)

 EDITORA
ARTEMIS
2025



O conteúdo deste livro está licenciado sob uma Licença de Atribuição Creative Commons Atribuição-Não-Comercial NãoDerivativos 4.0 Internacional (CC BY-NC-ND 4.0). Direitos para esta edição cedidos à Editora Artemis pelos autores. Permitido o download da obra e o compartilhamento, desde que sejam atribuídos créditos aos autores, e sem a possibilidade de alterá-la de nenhuma forma ou utilizá-la para fins comerciais.

A responsabilidade pelo conteúdo dos artigos e seus dados, em sua forma, correção e confiabilidade é exclusiva dos autores. A Editora Artemis, em seu compromisso de manter e aperfeiçoar a qualidade e confiabilidade dos trabalhos que publica, conduz a avaliação cega pelos pares de todos manuscritos publicados, com base em critérios de neutralidade e imparcialidade acadêmica.

Editora Chefe	Prof. ^a Dr. ^a Antonella Carvalho de Oliveira
Editora Executiva	M. ^a Viviane Carvalho Mocellin
Direção de Arte	M. ^a Bruna Bejarano
Diagramação	Elisangela Abreu
Organizador	Prof. Dr. Emilio Castro Otero
Imagem da Capa	yourapechkin/123RF
Bibliotecário	Maurício Amormino Júnior – CRB6/2422

Conselho Editorial

Prof.^a Dr.^a Ada Esther Portero Ricol, *Universidad Tecnológica de La Habana “José Antonio Echeverría”*, Cuba
Prof. Dr. Adalberto de Paula Paranhos, *Universidade Federal de Uberlândia*, Brasil
Prof. Dr. Agustín Olmos Cruz, *Universidad Autónoma del Estado de México*, México
Prof.^a Dr.^a Amanda Ramalho de Freitas Brito, *Universidade Federal da Paraíba*, Brasil
Prof.^a Dr.^a Ana Clara Monteverde, *Universidad de Buenos Aires*, Argentina
Prof.^a Dr.^a Ana Júlia Viamonte, *Instituto Superior de Engenharia do Porto (ISEP)*, Portugal
Prof. Dr. Ángel Mujica Sánchez, *Universidad Nacional del Altiplano*, Peru
Prof.^a Dr.^a Angela Ester Mallmann Centenaro, *Universidade do Estado de Mato Grosso*, Brasil
Prof.^a Dr.^a Begoña Blandón González, *Universidad de Sevilla*, Espanha
Prof.^a Dr.^a Carmen Pimentel, *Universidade Federal Rural do Rio de Janeiro*, Brasil
Prof.^a Dr.^a Catarina Castro, *Universidade Nova de Lisboa*, Portugal
Prof.^a Dr.^a Cirila Cervera Delgado, *Universidad de Guanajuato*, México
Prof.^a Dr.^a Cláudia Neves, *Universidade Aberta de Portugal*
Prof.^a Dr.^a Cláudia Padovesi Fonseca, *Universidade de Brasília-DF*, Brasil
Prof. Dr. Cleberton Correia Santos, *Universidade Federal da Grande Dourados*, Brasil
Dr. Cristo Ernesto Yáñez León – *New Jersey Institute of Technology*, Newark, NJ, Estados Unidos
Prof. Dr. David García-Martul, *Universidad Rey Juan Carlos de Madrid*, Espanha
Prof.^a Dr.^a Deuzimar Costa Serra, *Universidade Estadual do Maranhão*, Brasil
Prof.^a Dr.^a Dina Maria Martins Ferreira, *Universidade Estadual do Ceará*, Brasil
Prof.^a Dr.^a Edith Luévano-Hipólito, *Universidad Autónoma de Nuevo León*, México
Prof.^a Dr.^a Eduarda Maria Rocha Teles de Castro Coelho, *Universidade de Trás-os-Montes e Alto Douro*, Portugal
Prof. Dr. Eduardo Eugênio Spers, *Universidade de São Paulo (USP)*, Brasil
Prof. Dr. Eloi Martins Senhoras, *Universidade Federal de Roraima*, Brasil
Prof.^a Dr.^a Elvira Laura Hernández Carballido, *Universidad Autónoma del Estado de Hidalgo*, México
Prof.^a Dr.^a Emilas Darlene Carmen Lebus, *Universidad Nacional del Nordeste/ Universidad Tecnológica Nacional*, Argentina



Prof.ª Dr.ª Erla Mariela Morales Morgado, *Universidad de Salamanca*, Espanha
 Prof. Dr. Ernesto Cristina, *Universidad de la República*, Uruguay
 Prof. Dr. Ernesto Ramírez-Briones, *Universidad de Guadalajara*, México
 Prof. Dr. Fernando Hitt, *Université du Québec à Montréal*, Canadá
 Prof. Dr. Gabriel Díaz Cobos, *Universitat de Barcelona*, Espanha
 Prof.ª Dr.ª Gabriela Gonçalves, Instituto Superior de Engenharia do Porto (ISEP), Portugal
 Prof.ª Dr.ª Galina Gumovskaya – Higher School of Economics, Moscow, Russia
 Prof. Dr. Geoffroy Roger Pointer Malpass, Universidade Federal do Triângulo Mineiro, Brasil
 Prof.ª Dr.ª Gladys Esther Leoz, *Universidad Nacional de San Luis*, Argentina
 Prof.ª Dr.ª Glória Beatriz Álvarez, *Universidad de Buenos Aires*, Argentina
 Prof. Dr. Gonçalo Poeta Fernandes, Instituto Politécnico da Guarda, Portugal
 Prof. Dr. Gustavo Adolfo Juarez, *Universidad Nacional de Catamarca*, Argentina
 Prof. Dr. Guillermo Julián González-Pérez, *Universidad de Guadalajara*, México
 Prof. Dr. Håkan Karlsson, *University of Gothenburg*, Suécia
 Prof.ª Dr.ª Iara Lúcia Tescarollo Dias, Universidade São Francisco, Brasil
 Prof.ª Dr.ª Isabel del Rosario Chiyon Carrasco, *Universidad de Piura*, Peru
 Prof.ª Dr.ª Isabel Yohena, *Universidad de Buenos Aires*, Argentina
 Prof. Dr. Ivan Amaro, Universidade do Estado do Rio de Janeiro, Brasil
 Prof. Dr. Iván Ramon Sánchez Soto, *Universidad del Bío-Bío*, Chile
 Prof.ª Dr.ª Ivânia Maria Carneiro Vieira, Universidade Federal do Amazonas, Brasil
 Prof. Me. Javier Antonio Albornoz, *University of Miami and Miami Dade College*, Estados Unidos
 Prof. Dr. Jesús Montero Martínez, *Universidad de Castilla - La Mancha*, Espanha
 Prof. Dr. João Manuel Pereira Ramalho Serrano, Universidade de Évora, Portugal
 Prof. Dr. Joaquim Júlio Almeida Júnior, Unifimes - Centro Universitário de Mineiros, Brasil
 Prof. Dr. Jorge Ernesto Bartolucci, *Universidad Nacional Autónoma de México*, México
 Prof. Dr. José Cortez Godínez, Universidad Autónoma de Baja California, México
 Prof. Dr. Juan Carlos Cancino Díaz, Instituto Politécnico Nacional, México
 Prof. Dr. Juan Carlos Mosquera Feijoo, *Universidad Politécnica de Madrid*, Espanha
 Prof. Dr. Juan Diego Parra Valencia, *Instituto Tecnológico Metropolitano de Medellín*, Colômbia
 Prof. Dr. Juan Manuel Sánchez-Yáñez, *Universidad Michoacana de San Nicolás de Hidalgo*, México
 Prof. Dr. Juan Porras Pulido, *Universidad Nacional Autónoma de México*, México
 Prof. Dr. Júlio César Ribeiro, Universidade Federal Rural do Rio de Janeiro, Brasil
 Prof. Dr. Leinig Antonio Perazolli, Universidade Estadual Paulista (UNESP), Brasil
 Prof.ª Dr.ª Livia do Carmo, Universidade Federal de Goiás, Brasil
 Prof.ª Dr.ª Luciane Spanhol Bordignon, Universidade de Passo Fundo, Brasil
 Prof. Dr. Luis Fernando González Beltrán, *Universidad Nacional Autónoma de México*, México
 Prof. Dr. Luis Vicente Amador Muñoz, *Universidad Pablo de Olavide*, Espanha
 Prof.ª Dr.ª Macarena Esteban Ibáñez, *Universidad Pablo de Olavide*, Espanha
 Prof. Dr. Manuel Ramiro Rodríguez, *Universidad Santiago de Compostela*, Espanha
 Prof. Dr. Manuel Simões, Faculdade de Engenharia da Universidade do Porto, Portugal
 Prof.ª Dr.ª Márcia de Souza Luz Freitas, Universidade Federal de Itajubá, Brasil
 Prof. Dr. Marcos Augusto de Lima Nobre, Universidade Estadual Paulista (UNESP), Brasil
 Prof. Dr. Marcos Vinicius Meiado, Universidade Federal de Sergipe, Brasil
 Prof.ª Dr.ª Mar Garrido Román, *Universidad de Granada*, Espanha
 Prof.ª Dr.ª Margarida Márcia Fernandes Lima, Universidade Federal de Ouro Preto, Brasil
 Prof.ª Dr.ª María Alejandra Arecco, *Universidad de Buenos Aires*, Argentina
 Prof.ª Dr.ª Maria Aparecida José de Oliveira, Universidade Federal da Bahia, Brasil
 Prof.ª Dr.ª Maria Carmen Pastor, *Universitat Jaume I*, Espanha
 Prof.ª Dr.ª Maria da Luz Vale Dias – Universidade de Coimbra, Portugal
 Prof.ª Dr.ª Maria do Céu Caetano, Universidade Nova de Lisboa, Portugal

Prof.^ª Dr.^ª Maria do Socorro Saraiva Pinheiro, Universidade Federal do Maranhão, Brasil
 Prof.^ª Dr.^ª M^ªGraça Pereira, Universidade do Minho, Portugal
 Prof.^ª Dr.^ª Maria Gracinda Carvalho Teixeira, Universidade Federal Rural do Rio de Janeiro, Brasil
 Prof.^ª Dr.^ª María Guadalupe Vega-López, *Universidad de Guadalajara, México*
 Prof.^ª Dr.^ª Maria Lúcia Pato, Instituto Politécnico de Viseu, Portugal
 Prof.^ª Dr.^ª Maritza González Moreno, *Universidad Tecnológica de La Habana, Cuba*
 Prof.^ª Dr.^ª Maurícea Silva de Paula Vieira, Universidade Federal de Lavras, Brasil
 Prof. Dr. Melchor Gómez Pérez, Universidad del Pais Vasco, Espanha
 Prof.^ª Dr.^ª Ninfa María Rosas-García, Centro de Biotecnología Genómica-Instituto Politécnico Nacional, México
 Prof.^ª Dr.^ª Odara Horta Boscolo, Universidade Federal Fluminense, Brasil
 Prof. Dr. Osbaldo Turpo-Gebera, *Universidad Nacional de San Agustín de Arequipa, Peru*
 Prof.^ª Dr.^ª Patrícia Vasconcelos Almeida, Universidade Federal de Lavras, Brasil
 Prof.^ª Dr.^ª Paula Arcoverde Cavalcanti, Universidade do Estado da Bahia, Brasil
 Prof. Dr. Rodrigo Marques de Almeida Guerra, Universidade Federal do Pará, Brasil
 Prof. Dr. Saulo Cerqueira de Aguiar Soares, Universidade Federal do Piauí, Brasil
 Prof. Dr. Sergio Bitencourt Araújo Barros, Universidade Federal do Piauí, Brasil
 Prof. Dr. Sérgio Luiz do Amaral Moretti, Universidade Federal de Uberlândia, Brasil
 Prof.^ª Dr.^ª Silvia Inés del Valle Navarro, *Universidad Nacional de Catamarca, Argentina*
 Prof.^ª Dr.^ª Solange Kazumi Sakata, Instituto de Pesquisas Energéticas e Nucleares (IPEN)- USP, Brasil
 Prof.^ª Dr.^ª Stanislava Kashtanova, *Saint Petersburg State University, Russia*
 Prof.^ª Dr.^ª Susana Álvarez Otero – Universidad de Oviedo, Espanha
 Prof.^ª Dr.^ª Teresa Cardoso, Universidade Aberta de Portugal
 Prof.^ª Dr.^ª Teresa Monteiro Seixas, Universidade do Porto, Portugal
 Prof. Dr. Valter Machado da Fonseca, Universidade Federal de Viçosa, Brasil
 Prof.^ª Dr.^ª Vanessa Bordin Viera, Universidade Federal de Campina Grande, Brasil
 Prof.^ª Dr.^ª Vera Lúcia Vasilévski dos Santos Araújo, Universidade Tecnológica Federal do Paraná, Brasil
 Prof. Dr. Wilson Noé Garcés Aguilar, *Corporación Universitaria Autónoma del Cauca, Colômbia*
 Prof. Dr. Xosé Somoza Medina, *Universidad de León, Espanha*

Dados Internacionais de Catalogação na Publicação (CIP) (eDOC BRASIL, Belo Horizonte/MG)

O86g The Great World of Nanotechnology III / organização de Emilio Castro Otero. – 1. ed. – Curitiba, PR : Editora Artemis, 2025.

Formato: PDF

Requisitos de sistema: Adobe Acrobat Reader

Modo de acesso: World Wide Web

Edição bilingue.

Inclui bibliografia

ISBN 978-65-81701-79-6

DOI 10.37572/EdArt_121225796

1. Nanotecnologia biomédica. 2. Engenharia de tecidos. 3. Nanomateriais – Aplicações. 4. Biosistemas – Inovação tecnológica. 5. Sensores avançados – Desenvolvimento. I. Otero, Emilio Castro.

CDD 620.5

Elaborado por Maurício Amormino Júnior – CRB6/2422



FOREWORD

We are thrilled to present the third installment of ***The Great World of Nanotechnology***, a volume dedicated to exploring the cutting edge of nanotechnology applications, from the fundamental science of materials to their tangible impact on health, industry, and the environment. This book is meticulously structured into four thematic blocks, designed to guide the reader through the latest innovations that seek to solve crucial challenges in modern society.

The first pillar of this volume, ***Fundamentals of Nanomaterial Manufacturing and Characterization***, delves into the critical methodologies for creating high-quality nanostructures. Chapter 1 offers systematic research on the Effects of the Transfer Process on the Structure of Graphene Synthesized by Chemical Vapor Deposition. Complementing this, Chapter 2 examines Polymer Nanofibers via Airbrushing.

In ***Nanomaterials for Surface Engineering and Smart Sensors***, the chapters explore how these nanostructures can be applied in functional devices and material protection. Chapter 3 presents advances in the development of sensors based on graphene functionalized with nanoparticles. Similarly, Chapter 4 addresses the electrodeposition of nanostructured metal coatings.

Nanotechnology in Biomedical and Pharmaceutical Applications brings three chapters focusing on the use of nanotechnology to improve human health. Chapter 5 evaluates the Cytotoxic Effect of Nanoemulsion with Pumpkin Seed Oil on Breast Cancer Cell Lines. In the field of tissue engineering, Chapter 6 describes the development of Alginate/Collagen Structures Enhanced with Conductive Nanoparticles (PEDOT) for the Regeneration of Small-Diameter Blood Vessels. Finally, Chapter 7 discusses the development of an antiseptic gel based on bioactive compounds encapsulated in nanoparticles.

Concluding our exploration, ***Nanotechnological Solutions for Environmental Remediation*** addresses the water pollution crisis. The final chapter describes the Removal of Arsenic from Groundwater Using Recycled Iron Nanoparticles through the development of a low-cost filter that uses iron nanoparticles.

We invite you to immerse yourself in reading *The Great World of Nanotechnology*. Vol. III, where science on the smallest scale translates into large-scale solutions. We sincerely hope that this compilation of advanced research will not only be of utmost interest to you, but also inspire new directions of study and application in this infinitely promising field.

Emilio Castro Otero

PRÓLOGO

É com grande entusiasmo que apresentamos a terceira edição de ***The Great World of Nanotechnology***, um volume dedicado a explorar a vanguarda das aplicações nanotecnológicas, desde a ciência fundamental dos materiais até o seu impacto tangível na saúde, na indústria e no ambiente. Este livro está meticulosamente estruturado em quatro eixos temáticos, concebidos para guiar o leitor através das mais recentes inovações que procuram resolver desafios cruciais na sociedade moderna.

O primeiro eixo deste volume, ***Fundamentos da Fabricação e Caracterização de Nanomateriais***, aprofunda as metodologias críticas para a criação de nanoestruturas de alta qualidade. O Capítulo 1 oferece uma investigação sistemática sobre os Efeitos do Processo de Transferência na Estrutura do Grafeno Sintetizado por Deposição Química de Vapor e o segundo capítulo examina as Nanofibras Poliméricas via Aerografia.

Em seguida, o eixo ***Nanomateriais para Engenharia de Superfícies e Sensores Inteligentes***, explora como essas nanoestruturas podem ser aplicadas em dispositivos funcionais e proteção de materiais. O Capítulo 3 apresenta os avanços no desenvolvimento de Sensores Baseados em Grafeno Funcionalizado com Nanopartículas. Paralelamente, e o Capítulo 4 aborda a Eletrodeposição de Revestimentos Metálicos Nanoestruturados.

O eixo ***Nanotecnologia em Aplicações Biomédicas e Farmacêuticas***, centra-se na utilização da nanotecnologia para melhorar a saúde humana. O Capítulo 5 avalia o Efeito Citotóxico da Nanoemulsão com Óleo de Semente de Abóbora em Linhagens de Células de Cancro da Mama. No campo da engenharia de tecidos, o Capítulo 6 descreve o desenvolvimento de Estruturas de Alginato/Colagénio Melhoradas com Nanopartículas Condutoras (PEDOT) para a regeneração de Vasos Sanguíneos de Pequeno Diâmetro. Finalmente, o Capítulo 7 expõe a Elaboração de um Gel Antisséptico Baseado em Compostos Bioativos Encapsulados em Nanopartículas.

Concluindo a nossa exploração, o eixo ***Soluções Nanotecnológicas para Remédios Ambientais***, aborda a crise da contaminação da água. Este último capítulo descreve a Eliminação de Arsénico das Águas Subterrâneas Usando Nanopartículas de Ferro Reciclado, através do desenvolvimento de um filtro de baixo custo que utiliza nanopartículas de ferro.

Convidamo-lo a mergulhar na leitura de *The Great World of Nanotechnology Vol. III*, onde a ciência na escala mais pequena se traduz em soluções em grande escala. Esperamos sinceramente que esta compilação de pesquisas avançadas não só seja do seu interesse, mas também inspire novos rumos de estudo e aplicação neste campo infinitamente promissor.

Emilio Castro Otero

TABLE OF CONTENTS

FUNDAMENTALS OF NANOMATERIAL MANUFACTURING AND CHARACTERIZATION

CHAPTER 1..... 1

EFFECTS OF THE TRANSFER PROCESS ON THE STRUCTURE OF CVD-SYNTHESIZED GRAPHENE: A RAMAN SPECTROSCOPY STUDY

Rodrigo Segura-del-Río
Fernanda Olivares Salgado
Ricardo Henríquez Correa

 https://doi.org/10.37572/EdArt_1212257961

CHAPTER 2..... 15

NANOFIBRAS POLIMÉRICAS POR FIAÇÃO POR SOPRO EM SOLUÇÃO VIA AEROGRAFIA: UMA REVISÃO DAS PROPRIEDADES, VANTAGENS TECNOLÓGICAS E APLICAÇÕES EMERGENTES

Gabriel da Cruz Dias
Thelma Sley Pacheco Cellet
Mirian Cristina dos Santos
Caroline Silva Danna
Paulo Roberto Orlandi Ruiz
Deuber Lincon Agostini da Silva
Clarissa de Almeida Olivati

 https://doi.org/10.37572/EdArt_1212257962

NANOMATERIALS FOR SURFACE ENGINEERING AND SMART SENSORS

CHAPTER 3..... 34

SENSORES BASADOS EN GRAFENO FUNCIONALIZADO CON Pt-Sn/TiO₂ PARA DETECCIÓN DE SO₂

Luz María García-Rivera
Juan Manuel Padilla Flores
Octavio Maldonado Saavedra
Erick A. Juarez-Arellano

 https://doi.org/10.37572/EdArt_1212257963

CHAPTER 4..... 50

ELECTRODEPOSICIÓN DE RECUBRIMIENTOS METÁLICOS NANOESTRUCTURADOS

Marcos Bedolla Hernández

Genaro Texcucano Romano

Jorge Bedolla Hernández

Jorge Aguilar Vázquez

Carlos Alberto Mora Santos

Luz Fabiola Sánchez Parra

 https://doi.org/10.37572/EdArt_1212257964

NANOTECHNOLOGY IN BIOMEDICAL AND PHARMACEUTICAL APPLICATIONS

CHAPTER 5..... 60

CYTOTOXIC EFFECT OF PUMPKIN SEED OIL-LOADED NANOEMULSION IN BREAST CANCER CELL LINES

Anelise Pereira Alves

Wanderleya Toledo dos Santos

Daniel Augusto de Andrade

Felipe Kelmer Müller

Kézia Cristine Barbosa Ferreira

Guilherme Diniz Tavares

Fabiano Freire Costa

Paula Rocha Chellini

Ana Cláudia Chagas de Paula

 https://doi.org/10.37572/EdArt_1212257965

CHAPTER 6..... 74

ENHANCED ALGINATE/COLLAGEN SCAFFOLDS WITH CONDUCTIVE POLY (3,4-ETHYLENEDIOXYTHIOPHENE) NANOPARTICLES FOR NEXT-GENERATION SMALL-DIAMETER TISSUE-ENGINEERED BLOOD VESSELS

Emilio Castro

Èlia Bosch-Rué

Sara Estruch-Sotoca

Román A. Pérez

 https://doi.org/10.37572/EdArt_1212257966

CHAPTER 7 86

ELABORATION OF AN ANTISEPTIC GEL BASED ON BIOACTIVE COMPOUNDS OF *ORIGANUM VULGARE* AND *ALOE VERA* ENCAPSULATED IN SiO_2 Y ZnO-SnO_2 NANOPARTICLES FOR CONTROLLED RELEASE

Guadalupe Luna Cedillo
Francisco Javier Tzompantzi Morales
Sandra Luz Hernández-Valladolid
Juan Manuel Padilla Flores

 https://doi.org/10.37572/EdArt_1212257967

NANOTECHNOLOGICAL SOLUTIONS FOR ENVIRONMENTAL REMEDIATION

CHAPTER 8 96

ARSENIC REMOVAL FROM GROUNDWATER USING RECYCLED IRON NANOPARTICLES: DEVELOPMENT AND EVALUATION OF A LOW-COST FILTER FOR RURAL COMMUNITIES

Juan Simón Torres Espada
Yrene Romina Lazcano Cruz

 https://doi.org/10.37572/EdArt_1212257968

ABOUT THE ORGANIZER 106

INDEX 107

CHAPTER 7

ELABORATION OF AN ANTISEPTIC GEL BASED ON BIOACTIVE COMPOUNDS OF *ORIGANUM VULGARE* AND *ALOE VERA* ENCAPSULATED IN SiO_2 Y ZnO-SnO_2 NANOPARTICLES FOR CONTROLLED RELEASE

Data de submissão: 12/11/2025

Data de aceite: 28/11/2025

Juan Manuel Padilla Flores¹

1Universidad Tecnológica del
Centro de Veracruz
1Av. Universidad No.350
Carretera Federal Cuitláhuac-La Tinaja
Congregación dos Caminos
94910 Cuitláhuac
Veracruz – Llave, México
<http://orcid.org/0000-0002-9038-2959>

Guadalupe Luna Cedillo

Universidad Tecnológica del
Centro de Veracruz
1Av. Universidad No.350
Carretera Federal Cuitláhuac-La Tinaja
Congregación dos Caminos
94910 Cuitláhuac
Veracruz – Llave, México
<http://orcid.org/0000-0003-4876-0773>

Francisco Javier Tzompantzi Morales

Universidad Autónoma
Metropolitana – Iztapalapa
Departamento de Química
San Rafael Atlixco No. 186
México 09340, D.F., México
<http://orcid.org/0000-0002-3056-9500>

Sandra Luz Hernández-Valladolid

1Universidad Tecnológica del
Centro de Veracruz
1Av. Universidad No.350
Carretera Federal Cuitláhuac-La Tinaja
Congregación dos Caminos
94910 Cuitláhuac
Veracruz – Llave, México
<http://orcid.org/0000-0001-6962-6413>

ABSTRACT: The purpose of this project was to develop an antiseptic gel based on bioactive compounds of *Origanum vulgare* and *Aloe vera* incorporated with SiO_2 and $\text{ZnO} - \text{SnO}_2$ nanoparticles, to obtain a broad spectrum of bactericidal and virucidal action. Currently, in Mexico, the sanitary crisis caused by SARS-CoV-2 has had a significant impact on Mexican families, since hygiene and disinfection are the main concern of Mexicans. This problem has led the population to purchase antiseptic gels with a narrower spectrum of action, in order to reduce the cost of disinfection products. ZnO nanoparticles present antimicrobial properties, which together with SnO_2 nanoparticles, which have photocatalytic properties, generate a synergy. Likewise, the liberating properties of the SiO_2 nanoparticles show a better antimicrobial activity as a function of the antiseptic gel based on bioactive compounds of *Origanum vulgare* and *Aloe vera*.

KEYWORDS: antiseptics; nanoparticles; bactericidal; virucidal and bioactive compounds.

¹ Autor para correspondencia.

1. INTRODUCTION

Nanotechnology is the study and development of systems at the nanometer scale (1 nm is equivalent to 10^{-9} m), in which totally new properties and phenomena are observed, which are governed by the laws of quantum mechanics, these new properties are those that scientists take advantage of to create new materials (nanomaterials) or nanotechnological devices. Ortiz Aguilar (2019) explains that nanomaterials can occur naturally, however, there are also manufactured nanomaterials, which are intentionally designed with specific properties (mechanical, electrical, optical and catalytic) and these nanomaterials can be presented in the form of nano-objects, materials that are characterized by having one, two or three external dimensions at the nanoscale.

SiO_2 , SnO_2 and ZnO nanoparticles are nano-structured materials that have been studied for their properties, which include antibacterial action. For the fabrication of these nanomaterials, different synthesis methods have been used, either chemical or physical, which provide good properties.

In Mexico, the health crisis caused by SARS-CoV-2 had a significant impact on Mexican families, as the unemployment rate in Mexico increased, indicating a slow recovery of the country's economy. The Mexican population is applying sanitary measures to avoid contagion in their homes, with an estimated increase in the use of antiseptic gels in homes. However, due to the sanitary crisis, the prices of sanitizers, such as antiseptic gels, have risen, since hygiene and disinfection is the main concern of Mexicans. This problem leads the population to purchase antiseptic gels with a lower spectrum of action, in order to reduce the cost of disinfection products. On the other hand, there is a problem related to the epidemiology of wounds in Mexico. The health sector (2018) mentions the epidemiological characteristics and costs to wound care in medical units, as well as for the affected population in this area, since the prices of antiseptics present high costs for the treatment of acute and chronic wounds. It is estimated that 26.6% of the Mexican population presents traumatic injuries, and 23.4% corresponds to diabetic foot ulcers.

2. OBJECTIVE

To elaborate an antiseptic gel based on bioactive compounds of *Origanum vulgare* and *Aloe vera*, incorporated with SiO_2 and ZnO-SnO_2 nanoparticles, which allows having a broad bactericidal and virucidal spectrum to be used as a sanitary measure and improve the antimicrobial action against microorganisms present in wounds.

3. EXPERIMENTAL PART

3.1. OBTAINING THE AQUEOUS EXTRACT OF *ORIGANUM VULGARE*

Origanum vulgare leaves were collected on the federal highway in Fortín, Ver. The leaves were selected complete and free of pests. They were then washed with abundant tap water and the leaves were dried by dehydration for 6 h at 40°C in a smoking oven. Once dried, they were ground in a grinder. The crushed material was subjected to continuous extraction with 95% ethanol using the Soxhlet method. Finally, a simple distillation was performed to obtain the pure extract.

3.2. OBTAINING THE EXTRACT OF *ALOE VERA*

Aloe vera leaves were collected and selected homogeneously and representatively in shape, size and color, discarding those that showed damage or other alterations. The *Aloe vera* leaves were washed in a bath with water and sodium hypochlorite to eliminate microorganisms. Once the leaves were washed and dried, they were cut longitudinally on a tray, then with a spoon, the mucilage was gently scraped until it was completely separated from the cortical parenchyma, then the gel was stored in airtight containers.

3.3. PREPARATION OF NANOPARTICLES

SiO₂ nanoparticles

400 mL of distilled water and the surfactant were placed in an agitation of 700 rpm for 5 min. Subsequently, 16 mL of NH₄OH were added by drip, leaving the solution to agitate for 10 min. The temperature was raised to 95°C, leaving it to react by a constant agitation at 700 rpm. To maintain the temperature, a sand bath system was mounted. The product was then allowed to cool to room temperature. It was centrifuged at 15,000 rpm for 15 minutes with three washes of an ethanol-water solution (1:1). Once obtained, 15 mL of *Origanum vulgare* extract was added, allowing the mixture to rest. Subsequently, the mixture was placed in a water bath at 40°C until a pasty consistency was obtained. It was calcined at 400°C for 1h. At the end of the process of obtaining nanoparticles, a light green dry material was obtained.

SnO₂ nanoparticles

Two g of tin chloride (SnCl₂ · 2H₂O), used as tin precursor, was added to 42 mL of *Origanum vulgare* extract and left in agitation until its complete dissolution; obtaining a mixture. Subsequently, the sample was placed in a water bath at 60°C until a pasty

consistency was obtained. It was then calcined at 400°C for 60 min. At the end of the process, a dry light gray material was obtained.

ZnO nanoparticles

2 g of zinc nitrate was dissolved in 50 mL of distilled water in a beaker with constant stirring for 10 min, using a magnetic stirrer. After stirring, 5 mL of *Origanum vulgare* extract was added. The mixture was heated from 60°C to 90°C. The color of the resulting solution changed from a transparent white to a light green paste confirming the formation of ZnO NPs. The obtained paste was transferred to a ceramic crucible and kept in a muffle furnace heated at 400°C for 2h. The resulting powder was used for characterization and preparation of the antiseptic gel.

3.4. CHARACTERIZATION OF NANOPARTICLES

UV-Vis Spectroscopy Analysis

UV-Visible spectrophotometer was used to confirm the formation of SiO₂, SnO₂ and ZnO nanoparticles. The UV-Vis spectra of the samples were performed in Perkin Elmer spectrophotometer, in the range of 200 to 800 nm.

3.5. PREPARATION OF ANTISEPTIC GEL BASE

2 g of carbopol were dissolved in 120 mL of alcohol in a beaker with a stirring of less than 150 rpm. Subsequently, 2 mL of glycerin was added, maintaining a constant agitation. When the mixture was homogenized, 1 mL of trihydroxyethylamine was added. Finally, when the gel obtained consistency, it was bottled.

3.6. PREPARATION OF AN ANTISEPTIC GEL BASED ON NATURAL EXTRACTS AND NANOPARTICLES

2 g of carbopol were dissolved in 120 mL of alcohol in a beaker with a stirring of less than 150 rpm. Subsequently, 2 mL of glycerin was added, maintaining a constant agitation. When the mixture was homogenized, 1 mL of trihydroxyethylamine and 5 mL of *Aloe vera* extract were added. After the gel obtained consistency, it was packaged. To impregnate the SiO₂ and ZnO - SnO₂ nanoparticles, a sonicator was used with a duration of 30 min. Finally, the gel samples were left to rest.

3.7. PREPARATION OF CULTURE MEDIA

In the preparation of the culture media using nutrient agar, 23 g of the medium was rehydrated in 1L of distilled water. It was then allowed to stand for 10 to 15 min. Once

rested, it was heated at constant stirring to boiling point for 1 min to dissolve it completely. It was then autoclaved at 121°C for 15 min.

In casein peptone culture media, 20 g of the medium was rehydrated in 1 L of distilled water. It was then allowed to stand for 15 to 20 min. Once resting, it was heated by stirring constantly to boiling point for 2 min to dissolve completely. It was then sterilized in autoclave at 121°C for 17 min.

Once sterilization was complete, the media were poured into each of the corresponding petri dishes, where they were allowed to cool to room temperature. Finally, the media were labeled for use in other tests.

3.8. DETERMINATION OF ANTIMICROBIAL ACTIVITY

To analyze the antimicrobial activity of the antiseptic gel based on extracts with the incorporation of SiO_2 and SnO_2 - ZnO nanoparticles, disc diffusion methods were performed, where gram-positive and gram-negative bacterial species were used. The sterile discs loaded with different concentrations of nanoparticles solution (1 mg/ mL) were aseptically maintained in petri dish media, previously cleaned with a broth solution of test bacteria.

In addition, the base antiseptic gel was used as a positive control, while samples of the natural extract-based antiseptic gel with the incorporation of nanoparticles were used as negative controls. The antimicrobial activity was scored in the clear zones surrounding the corresponding discs.


4. RESULTS AND DISCUSSION

4.1. UV-VIS SPECTROSCOPY ANALYSIS

SiO_2 nanoparticles

The SiO_2 nanoparticles were analyzed using UV-Vis spectroscopy in the range between 300 to 800 nm. In Figure 1, the peak absorbance of these nanoparticles is observed at 350 nm, due to their surface plasmon resonance.

Figure 1. UV-Vis spectroscopy of the SiO_2 .

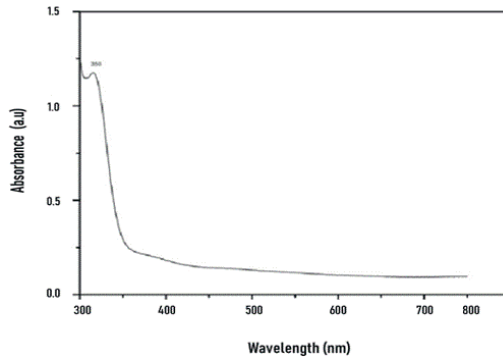

SnO_2 nanoparticles

UV-Vis spectroscopy analysis was performed at room temperature. The absorption spectrum of SnO_2 nanoparticles was recorded in a wavelength range between 200 to 800 nm. In Figure 2, the absorbance peak of SnO_2 nanoparticles at 260 nm is observed. The energy value of the forbidden band is 2.84 eV.

ZnO nanoparticles

The confirmation of *Origanum vulgare* extract of ZnO nanoparticles was observed by the color change from white to light green. In Figure 3, the UV spectrum of the synthesized ZnO nanoparticles is shown. The absorbance peak is at 354 nm, due to the surface plasmon resonance of these nanoparticles.

Figure 2. UV-Vis spectroscopy of the SnO_2 .


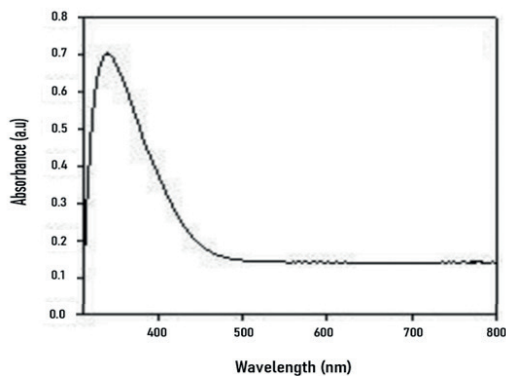


Figure 3. UV-Vis spectroscopy of the ZnO.

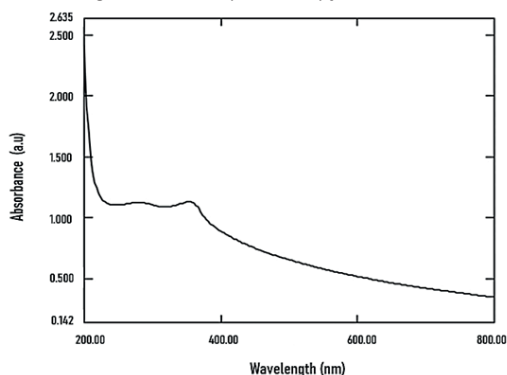


4.2. DETERMINATION OF ANTIMICROBIAL ACTIVITY OF ANTISEPTIC GEL

The nanoparticles used for the preparation of the antiseptic gel are used in various applications due to their antimicrobial properties. In the present study, agar disc diffusion test was used to measure the efficiency of the antiseptic gel based on natural extracts with the incorporation of SiO_2 and $\text{ZnO} - \text{SnO}_2$ nanoparticles against gram negative and gram positive bacteria. The inhibition zone was analyzed by the disk diffusion method for 4 h with the corresponding nanoparticles, using different concentrations for the preparation of the antiseptic gel.

Figure 4 shows the antimicrobial activity of the antiseptic gel samples, in the case of Figure 4(a) it can be determined that the base gel presents a superficial antimicrobial activity against the positive bacteria, this is attributed to the large surface area to volume ratio of the nanoparticles used, providing a better inhibitory contact with the microorganisms. The antimicrobial properties of the nanoparticles interact with the microorganisms by adhering to the surface of the bacterial cell membranes, penetrating and affecting the permeability of the bacterial membranes.

Figure 4. Antimicrobial activity (a) base gel and (b) antiseptic gel with ZnO-SnO_2 nanoparticles.

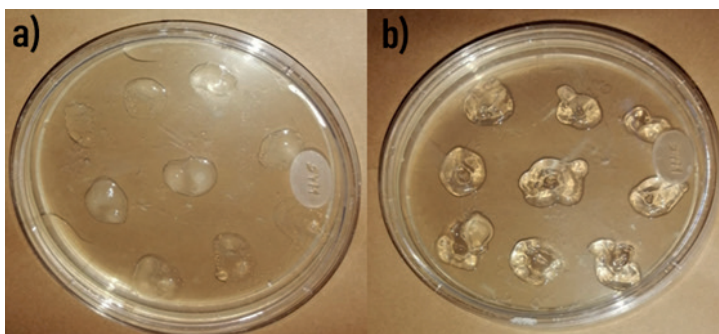

Tables 1 and 2 show the size of the disinfected diameter using the antiseptic gel based on natural extracts with the incorporation of SiO_2 and $\text{ZnO} - \text{SnO}_2$ nanoparticles.

Table 1. Recording of the diameter of the disinfected área of the ZnO-SnO_2 nanoparticles

Registro de área desinfectada (mm)				
	1 h	2 h	3 h	4 h
Blanco	5 mm	6 mm	7 mm	8 mm
0.25 g / L	5 mm	7 mm	9 mm	11 mm
0.5 g / L	9 mm	10 mm	15 mm	17 mm
1 g / L	10 mm	11 mm	14 mm	17 mm

Table 1 shows the records regarding the diameter of the disinfection area using ZnO-SnO_2 nanoparticles in the antiseptic gel samples. The record of the disinfection area was recorded in millimeters. As can be seen in the table, the antiseptic gel without the bioactive components of *Origanum vulgare* and *Aloe vera* extracts with the incorporation of nanoparticles at different concentrations, presented a lower area than the samples of the antiseptic gel incorporated by natural extracts already mentioned and ZnO-SnO_2 nanoparticles.

The study to evaluate the effectiveness of the antiseptic gel had a duration of 4 h, where the samples showed an effectiveness in reducing microorganisms present in the medio de cultivo of gram-negative and gram-positive.

The sample with a concentration of 0.5 g/L showed a higher effectiveness in the antimicrobial activity on gram-negative and gram-positive bacteria. However, the samples with a concentration of 1 g/L of ZnO-SnO_2 nanoparticles also presented a greater effectiveness, however, there was not a great difference with respect to the samples with a concentration of 0.5 g/L, which is why it was analyzed that this concentration allows a prolonged release of the bioactive compounds of the *Origanum vulgare* and *Aloe vera* extracts.

Table 2. Recording of the diameter of the disinfected of the SiO_2 nanoparticles.

Registro de área desinfectada (mm)				
	1 h	2 h	3 h	4 h
Blanco	5 mm	6 mm	7 mm	8 mm
0.25 g / L	5 mm	6 mm	8 mm	9 mm
0.5 g / L	5 mm	7 mm	8 mm	10 mm
1 g / L	6 mm	8 mm	9 mm	11 mm

Table 2 shows the record corresponding to the antimicrobial evaluation of the antiseptic gel based on the bioactive components of *Origanum vulgare* and *Aloe vera* extract with different concentrations of SiO_2 nanoparticles with respect to the antiseptic gel without components, which was considered as a blank.

The sample that presented the best effectiveness for the reduction of microorganisms was the one with the concentration of 1 g/L of SiO_2 nanoparticles with the bioactive compounds of the *Origanum vulgare* and *Aloe vera* extracts. However, this sample did not present the same effectiveness with both gram-negative and gram-positive microorganisms.

5. CONCLUSIONS

UV-Vis spectroscopy confirmed the formation of SiO_2 , ZnO and SnO_2 nanoparticles.

The study of the antimicrobial activity showed that the antiseptic gel based on *Origanum vulgare* and *Aloe vera* extract with the incorporation of 0.5 g/L of $\text{ZnO} - \text{SnO}_2$ nanoparticles developed a synergy, increasing the efficiency of the antimicrobial activity due to its photocatalytic properties, allowing the reduction of gram-negative and gram-positive bacteria.

The release character of SiO_2 can be observed through the increase of the inhibition area with respect to the release of *Origanum vulgare* and *Aloe vera* extracts over time.

Therefore, it is concluded that the antiseptic properties of alcohol, as well as those of *Origanum vulgare* and *Aloe vera* extracts, the SiO_2 releasing character, and the photoactive properties of ZnO-SnO_2 , present a synergy resulting in a better antimicrobial activity.

6. ACKNOWLEDGMENTS

Agradecemos a la Universidad Tecnológica del Centro de Veracruz, por todo el apoyo brindado y por permitirnos el uso de su infraestructura para desarrollar este proyecto. Asimismo, le agradecemos al Dr. Vicente Rodríguez González del Instituto Potosino de Investigación Científica y Tecnológica A.C. (IPICYT), como también al Dr. Francisco Javier Tzompantzin Morales del departamento de Química de la Universidad Autónoma Metropolitana (UAM).

BIBLIOGRAPHIC REFERENCES

Ortiz Aguilar, J. E. (2019). *Actividad antimicrobiana de nanopartículas cerámicas sintetizadas por un método verde para uso en aplicaciones biomédicas*. [Tesis de grado, Universidad Autónoma de Occidente]. <https://red.uao.edu.co/bitstream/handle/10614/11795/T08856.pdf?sequence=6&isAllow>

Morales, R., Pascual, H. y Tandío, J. (2004). *Jardín Botánico de Madrid*. Ibersaf.

Arcila, C., Loarca, G., Lecona, S. y González, E. (2004). Oregano: Properties, composition and biological activity. *Scielo*, 54(1), 100 – 111. http://ve.scielo.org/scielo.php?script=sci_arttext&pid=S

López, D. (2019). Identification of possible toxicological risks and their sanitary regulations of the use of nanomaterials in products for human consumption in Mexico. *Revista Médica*, 10(3), 221 – 228. <https://www.medigraphic.com/pdfs/revmed/md-2019/md193e.pdf>

Rodrigues, M., Kosaric, N., Bonham, C. y Gurtner, G. (2019). Wound healing: A cellular perspective. *Physiological reviews*, 99(1), 665-706. <https://doi.org/10.1152/physrev.00067.2017>

Wang, P., Huang, B., Horng, H., Yeh, C. y Chen, Y. (2018). Wound healing. *Journal of the Chinese Medical Association: JCMA*, 81(2), 94-101. <https://doi.org/10.1016/j.jcma.2017.11.002>

ABOUT THE ORGANIZER

Emilio Castro Otero é professor da área de Bioengenharia na *Universitat Internacional de Catalunya*, Barcelona, Espanha. Pesquisador com ampla trajetória científica nas áreas de biomateriais, nanotecnologia, química física de polímeros e sistemas nanoestruturados aplicados à medicina regenerativa e à liberação controlada de fármacos. Sua produção abrange estudos fundamentais sobre auto-organização molecular, interações entre copolímeros e surfactantes, estabilidade proteica e desenvolvimento de nanopartículas e hidrogéis inteligentes, contribuindo de maneira significativa para a compreensão dos mecanismos físico-químicos que governam materiais avançados e sua aplicabilidade biomédica. Seu trabalho mais recente, publicado em *Acta Biomaterialia* (2023), aborda o papel angiogênico e imunomodulador de íons nas fases iniciais da regeneração óssea, consolidando sua atuação no campo dos biomateriais bioativos. Ao longo de sua carreira, publicou artigos de impacto em periódicos como *Langmuir*, *Biomacromolecules*, *Journal of Biomedical Nanotechnology*, *Macromolecular Bioscience*, *Journal of Physical Chemistry B*, *Chemical Physics* e *Journal of Colloid and Interface Science*, além de contribuir com capítulo de livro na área de nanomedicina, ampliando sua presença internacional na literatura científica.

Entre suas contribuições relevantes, destacam-se estudos sobre auto-organização de elastina recombinante e copolímeros responsivos à temperatura, síntese e caracterização de nanopartículas funcionalizadas, incluindo magnetita pegulada e nanocápsulas multifuncionais, e sistemas poliméricos capazes de encapsular e liberar fármacos de forma controlada, com foco em aplicações oncológicas e terapêuticas avançadas. Sua pesquisa também inclui extensas investigações termodinâmicas envolvendo surfactantes, copolímeros e sistemas micelares complexos, bem como análises detalhadas de interações entre proteínas e fármacos anfífilicos, contribuindo para o entendimento de processos de dobramento, estabilidade e agregação proteica. Com forte perfil interdisciplinar, o pesquisador tem colaborado com grupos internacionais de renome em bioengenharia, físico-química de materiais, nanotecnologia e biotecnologia aplicada, contribuindo para o desenvolvimento de estratégias inovadoras em engenharia de tecidos, medicina regenerativa e materiais biomiméticos.

Ao longo de quase duas décadas de produção científica contínua, Emilio Castro Otero consolidou uma carreira marcada pela investigação rigorosa, inovação metodológica e abordagem integrada da ciência dos materiais, oferecendo contribuições relevantes tanto para o avanço do conhecimento fundamental quanto para o desenvolvimento de soluções tecnológicas com potencial translacional na área biomédica.

ORCID: <https://orcid.org/0000-0002-7491-4169>

INDEX

A

Adsorption 13, 80, 96, 97, 98, 100, 101, 102, 103, 104, 105

Aerografia 15, 16, 17, 18, 21, 22, 23, 25, 26, 27

Antiseptics 86, 87

Arsenic 96, 97, 98, 99, 100, 101, 102, 103, 104, 105

B

Bactericidal 86, 87

Blood vessel 75, 84

C

Chemical vapor deposition 1, 14

Conductive hydrogel 75

Cromo 50, 51, 53, 54, 58, 59

Cucurbita moschata 60, 61, 62, 63, 68, 70, 71, 72, 73

E

Electrodeposición 50, 51, 52, 53, 54, 55, 56

Emulsions 61, 63, 64, 73

F

Fiação por Sopro de Solução 16, 22, 24, 30

G

Graphene 1, 2, 3, 4, 5, 6, 7, 8, 9, 10, 11, 12, 13, 14, 27, 31, 34, 35

Graphene transfer 1, 4, 9

Groundwater 96, 97, 98, 99, 105

I

Inflammatory breast neoplasms 61

Iron nanoparticles 96, 100, 101, 104, 105

Iron oxide 96, 97, 100, 101, 102, 104, 105

L

Low-cost filter 96

M

Morfología 22, 24, 33, 47, 51, 53, 56, 57

N

Nanocompuesto 34, 36, 37, 38, 43, 47

Nanofibras 15, 16, 17, 18, 19, 20, 21, 22, 24, 25, 26, 27, 30, 32

Nanoparticles 32, 35, 51, 62, 69, 72, 74, 75, 77, 78, 80, 81, 82, 83, 85, 86, 87, 88, 89, 90, 91, 92, 93, 94, 96, 97, 100, 101, 102, 103, 104, 105

Nanopartículas de óxidos metálicos 34

Nanopartículas metálicas 51, 52

O

Óxido de grafeno 34, 36, 39, 40, 48, 49

P

PEDOT nanoparticles 74, 75, 77, 78, 81, 82, 83

Propiedades poliméricas 16

R

Raman spectroscopy 1, 5, 11, 13, 14, 35

Recubrimientos nanoestructurados 50, 51, 53, 59

S

Sensores de gas 34, 36

Smooth muscle cells 74, 75, 82, 84

T

Toxicity tests 61

Tratamento de água 15, 16, 17, 18, 25, 26

V

Vascular regeneration 74, 75, 83

Virucidal and bioactive compounds 86

